

## A COMPARISON OF SPONTANEOUS COMBUSTION SUSCEPTIBILITY OF COAL FROM THE BENUE TROUGH ACCORDING TO RANK

**M. U. Uzoegbu, A. C. Ibe and F. T. Beka**

*Department of Geology, Faculty of Physical Science and Information Technology,  
College of Natural and Applied Sciences,  
University of Port Harcourt, Port Harcourt, Nigeria.  
E-mail: [uche.uzoegbu@uniport.edu.ng](mailto:uche.uzoegbu@uniport.edu.ng) OR [muuzoegbu@yahoo.com](mailto:muuzoegbu@yahoo.com)*

*Received: 27-03-15*

*Accepted: 28-04-15*

### **ABSTRACT**


*This study investigated spontaneous combustion susceptibility of coal according to the rank. To estimate the spontaneous combustion susceptibility of coal, both crossing-point temperature (CPT) measurement and gas analysis by using gas chromatography (GC) were performed. For the experiment, Ihuoma coal, Orlu lignite, and Onyeama coal and Owukpa coal that are sub-bituminous coal, Obi/Lafia bituminous coal was used. The lignite such as Ihuoma coal contains more functional groups that easily react to oxygen more so than Onyeama and Owukpa coals. Also, Onyeama and Owukpa coal more functional groups than Obi/Lafia coal. For this reason, the lignite is more easily oxidized than sub-bituminous coal and sub-bituminous more easily oxidized than bituminous at low temperature, which results in high O<sub>2</sub> consumption, increase in CO and CO<sub>2</sub> generation, and low CPT. Although the CPT of Onyeama coal and Owukpa coal is identical to each other as they are the sub-bituminous, Owukpa coal has a lower initial oxidation temperature (IOT) and maximum oxidation temperature (MOT) than those of Onyeama coal. This means that although each coal has the same rank and CPT, spontaneous combustion susceptibility of coal may vary because the initial temperature of the coal at which oxidation begins may be different due to the substances that participate in oxidation.*

**Key Words:** Coal rank, cross-point-temperature, spontaneous combustion, low temperature oxidation.

### **INTRODUCTION**

The spontaneous combustion susceptibility of coal causes difficulties in transporting, sorting, and using coal, which is critical in terms of safety and economy (Goodarzi and Gentzis, 1991; Wei et al., 2013). Several methods are available to determine the spontaneous combustion susceptibility of coal, such as adiabatic oxidation (Banerjee, 1985); high temperature activation energy (Münzner and Peters, 1965; Banerjee, 1985;

Postzednik et al., 1988); crossing-point temperature (Oresko, 1959; Banerjee, 1985; Handa et al., 1985; Kaymakçi and Didari, 2002); and gas analysis methods (Lang and Fu-bao, 2010; Xie et al., 2011). Crossing point temperature (CPT), average heating rate (AHR) and slope of the time-temperature curve on the crossing point (CPS) (Fig. 1) are taken as the spontaneous combustion parameters.

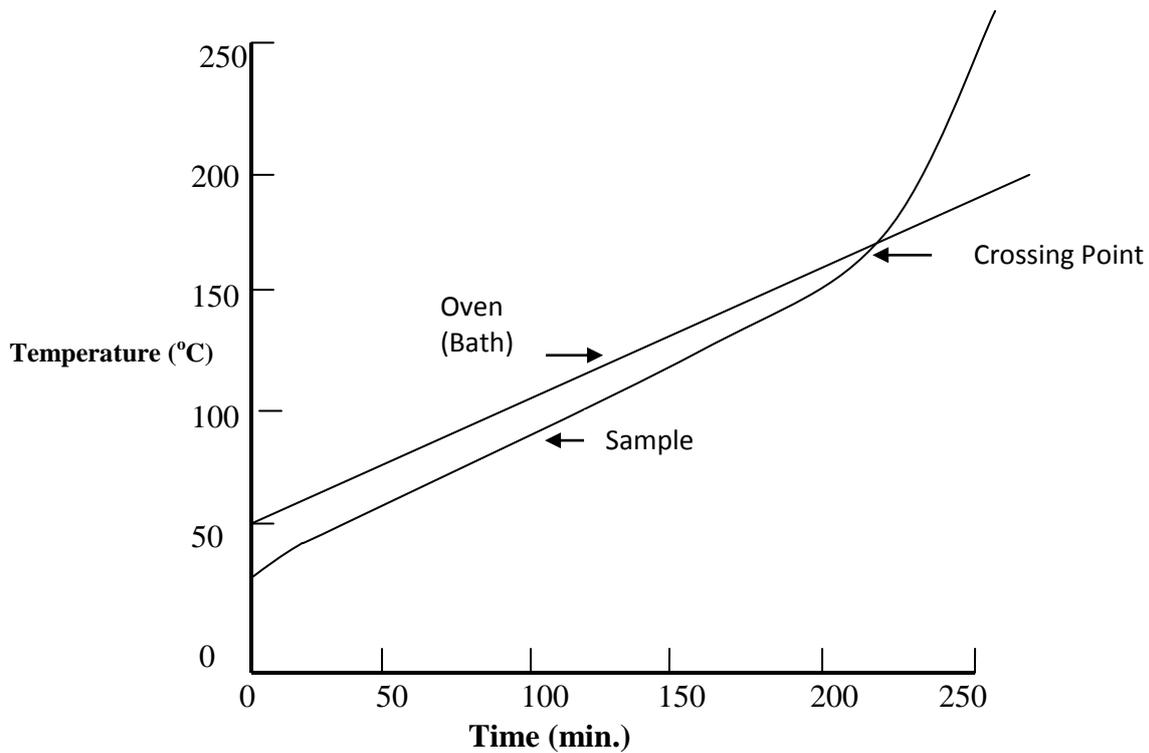

**Fig. 1: Time – temperature curve (modified from Kaymakçı and Didari, 2002).**

If air or oxygen is supplied in the oven that contains the coal by increasing the temperature inside the oven, the temperature of the coal will increase along with the temperature of the oven, and at a certain point, the coal temperature will exceed the oven temperature due to self-heating through the oxidation of coal. This point at which the coal temperature crosses that of the oven is called crossing-point temperature (CPT).

Research on CPT measurement was first done by Postzednik et al. (1988). CPT measurement has been used for evaluating spontaneous combustion susceptibility of coal. CPT measurement in previous studies was conducted according to coal properties such as rank, particle size, moisture content, and application conditions such as the flow rate of oxygen, heating rate, and the amount coal samples (Oresko, 1959; Banerjee,

1985; Handa et al., 1985; Kaymakçı and Didari, 2002). Since CPT measurement methods measures the temperature of part of all coal contained in the vessel, it may decrease the reliability of the results due to the property of coal that is not a single substance.

Gas analysis using gas chromatography (GC) is used to estimate spontaneous combustion susceptibility of coal through analysis the concentration of CO and CO<sub>2</sub> that is generated when coal reacts with oxygen and the oxygen consumption (Goodarzi and Gentzis, 1991; Lang and Fubao, 2010; Xie et al., 2011). In general, the higher the spontaneous combustion susceptibility of coal the more temperature (Kröger and Beier, 1962; Güney, 1968; Chamberlain and Hall, 1973a; Feng et al., 1973; Beier, 1973; Kim, 1977; Banerjee, 1982; Didari, 1988; Goodarzi and Gentzis,

1991; Didari and Ökten, 1994; Lang and Fu-bao, 2010; Xie et al., 2011).

By combining the CPT measurement and GC analysis method, we can analyze the spontaneous combustion susceptibility of coal and compliment any short-coming that only we can measure the part of coal temperature during CPT measurement.

In this study, we measured CPT of two ranks of coal samples from three locations in Benue Trough (Fig. 2) made up of lignite and sub-bituminous in order to estimate the spontaneous combustion susceptibility of coal according to rank. In the process, we analyzed the CO and CO<sub>2</sub> concentration that generated in the process by using the GC. During the experiments, we fixed the factors that affect the result of CPT measurement:

gas flow rate, heating rate; moisture content, and size of the coal.

In this paper we assess coal samples from three regions in the Benue Trough (Fig. 2). The Benue Trough geographically subdivided into Southern, Central, and Northern Benue Trough is strictly a sedimentary basin extending from the Gulf of Guinea in the south to the Chad Basin in the north (Offodile, 1976; Dike, 1976a,b, 1993, 2002; Adeleye and Fayose, 1978; Enu, 1987 and Petters, 1978, 1979b, 1980, 1982, 1991). The origin and tectonic history of the Benue Trough is associated with the break-up of the continents of Africa and South America. This break-up was followed by the drifting apart of these continents, the opening of the South Atlantic, and the growth of the mid-Atlantic ridge (Read and Watson, 1978; Freeth, 1990).

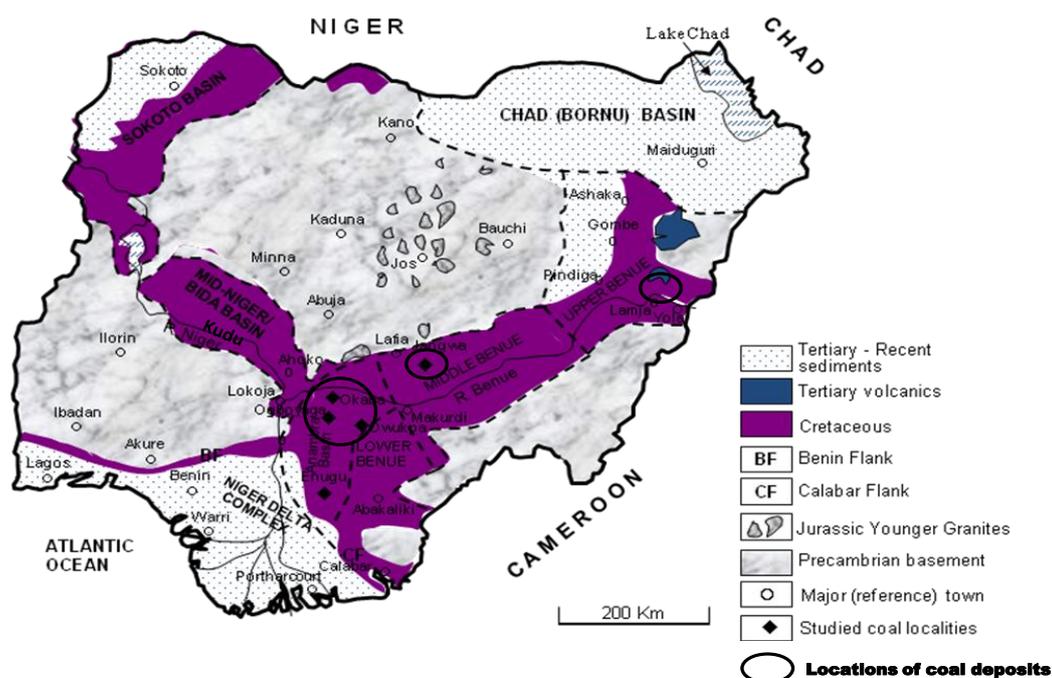


Fig. 2: Generalized geological map of Nigeria showing some coal deposit locations and locations of studied coal deposits

### **Synopsis of the Geology of the Benue Trough**

The Benue Trough of Nigeria is a rift basin in central West Africa that extends NNE – SSW for about 800 km in length and 150 km in width (Fig. 1). The trough contains up to 6000m of Cretaceous – Tertiary sediments of which those pre-dating the mid-Santonian have been compressionaly deformed, faulted and uplifted in several places. Compressional folding during the mid-Santonian tectonic episode affected the whole of the Benue Trough and was quite intense, producing over 100 anticlines and synclines (Benkhelil, 1989). Following mid-Santonian tectonism and magmatism, depositional axis in the Benue Trough was displaced westward resulting in subsidence of the Anambra basin. The Anambra basin, therefore, is a part of the Southern Benue Trough containing post-deformational sediments of Campano – Maastrichtian to Eocene ages. It is logical to include the Anambra basin in the Benue Trough, being a related structure that developed after the compressional stages (Akande and Erdtmann, 1998). The Benue trough is subdivided into a Southern, Central and an Northern portion (Figs. 2, 3 and 4). A generalized stratigraphic succession in the Benue Trough and the relationship to the Chad basin and the Niger Delta is given on Figs. 3 and 4. Details on the geology and stratigraphy of the Benue trough have been comprehensively discussed, reviewed and presented by Carter et al. (1963), Whiteman, (1982), Akande et al. (1998), Obaje et al. (1999), Obaje and Hamza (2000), Pearson and Obaje (2000) and Obaje et al. (2004), amongst others.

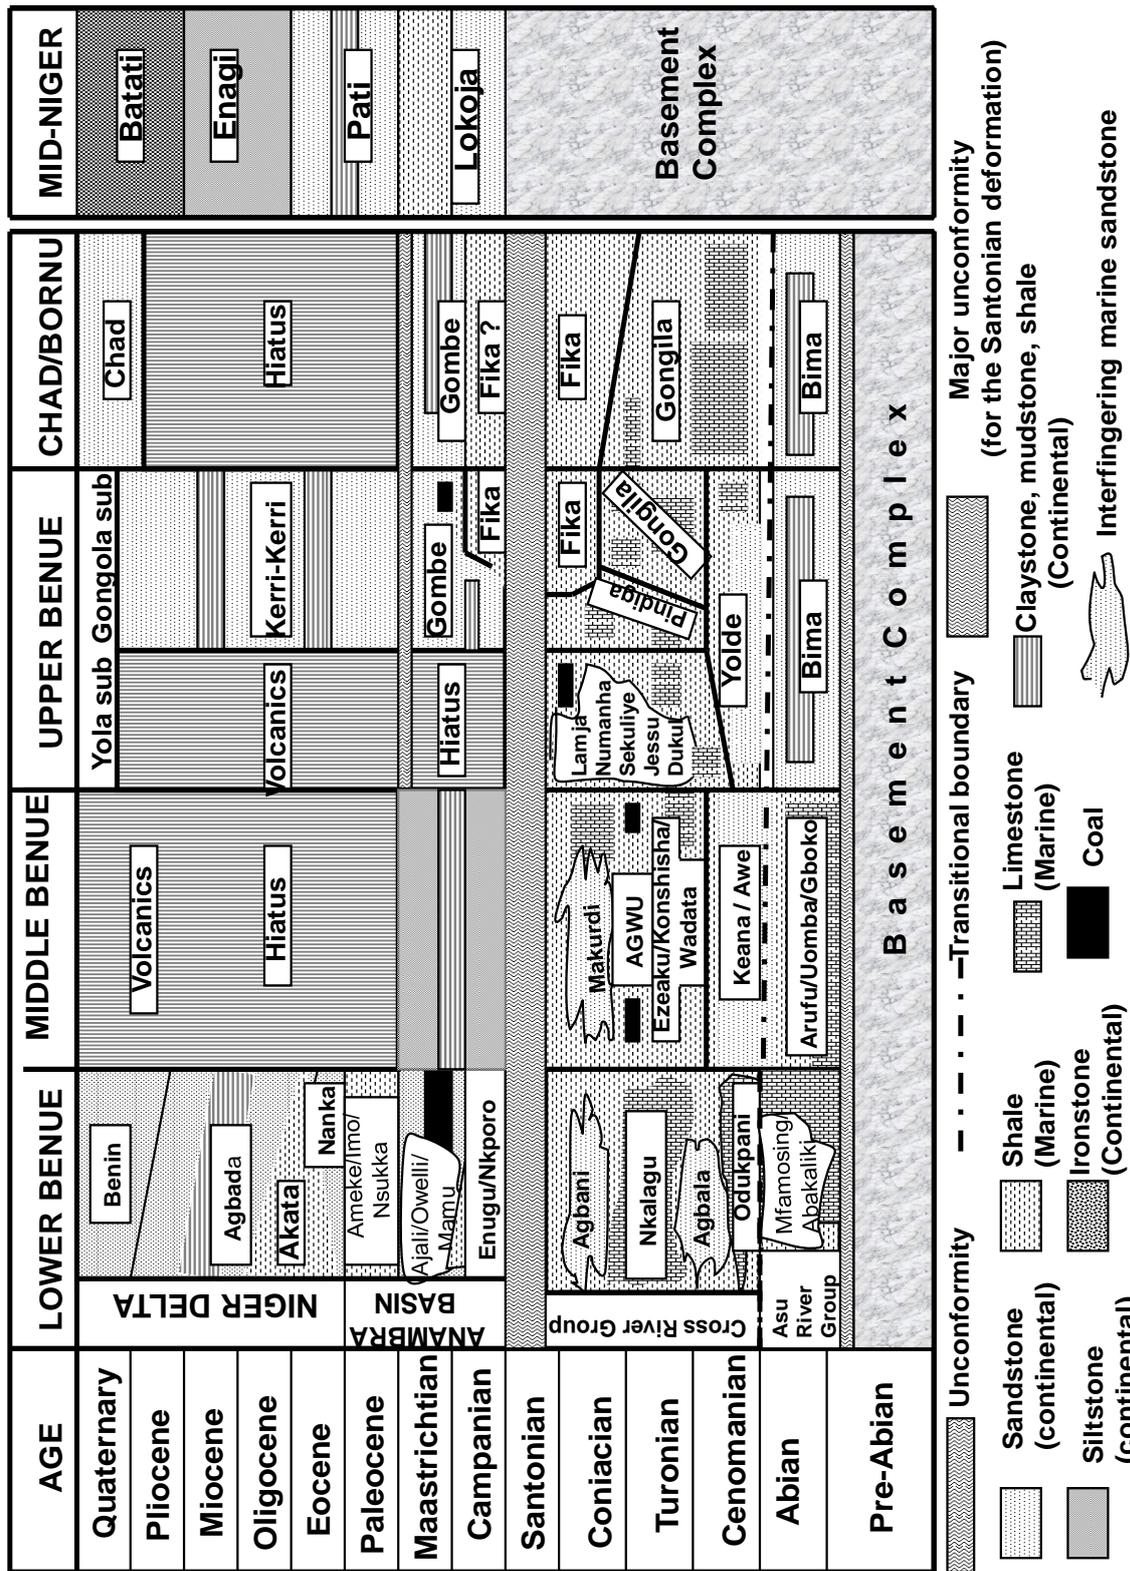


Fig. 3: Stratigraphic succession in the Benue trough, the Nigerian sector of the Chad Basin, the Mid-Niger Basin and relationship to the Nialer delta (after Obaie et al., 2006).

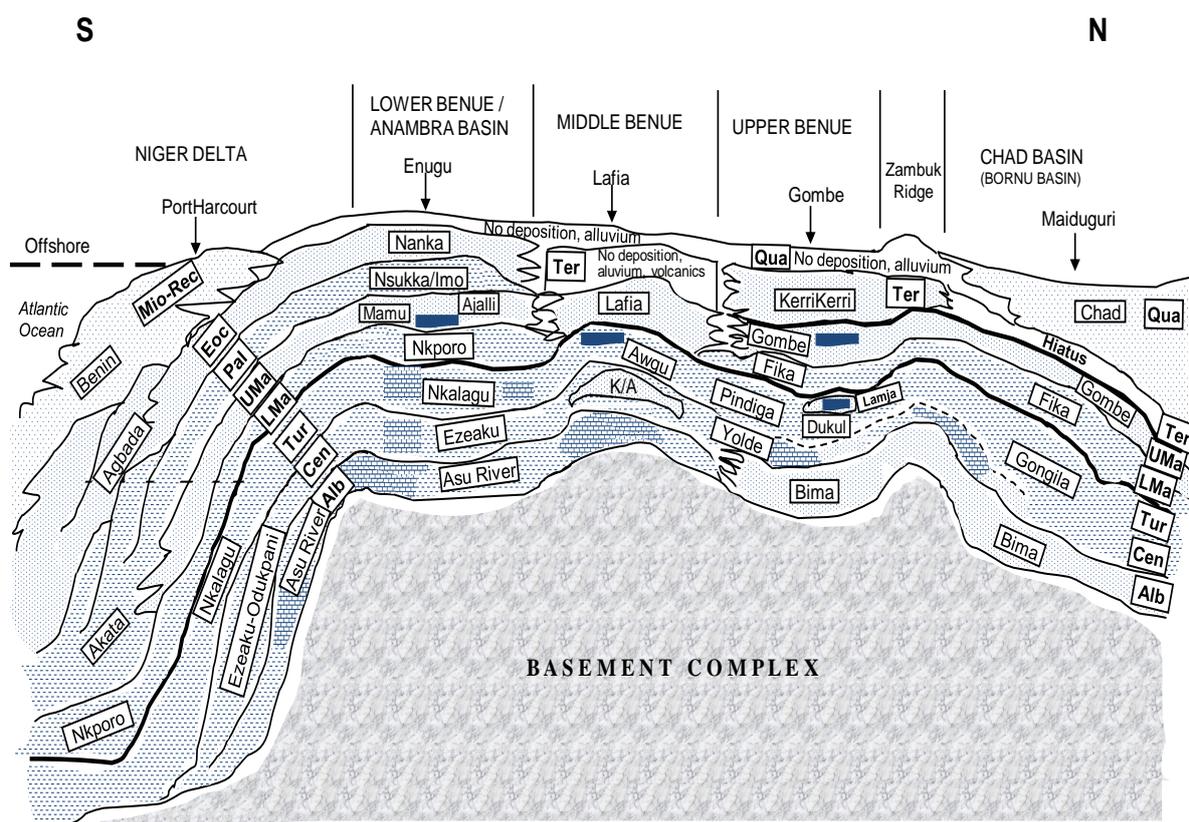


Fig. 4: Idealized N-S stratigraphic cross-section across the Benue Trough and the relationship to the Niger Delta and the Chad Basin (vertical scale exaggerated; erosion and uplift not considered, after Obaje et. al, 2004).

## EXPERIMENTAL

### Coal Sample

Ihuoma coal samples, which is lignite, Onyeama and Owukpa coal that are, sub-bituminous and Obi/Lafia coal of bituminous coal were used in this study. Among the coals selected lump coal that was more than 10cm in diameter was selected for the samples to minimize the effect of weathering. The lump coal was crushed and sieved in order to obtain particles that were 180-425  $\mu\text{m}$  in size for use. To remove any effect caused by

moisture during the CPT measurement, the coal was dried at 107°C under a nitrogen atmosphere for 12 hours.

### Experimental Apparatus and Procedure

A conceptual diagram of the CPT measurement apparatus used in the experiment is shown in Fig. 5. Two vessels that contain a coal sample are located inside an oven in which the temperature is programmable. To each vessel, nitrogen or air is selectively supplied pass through

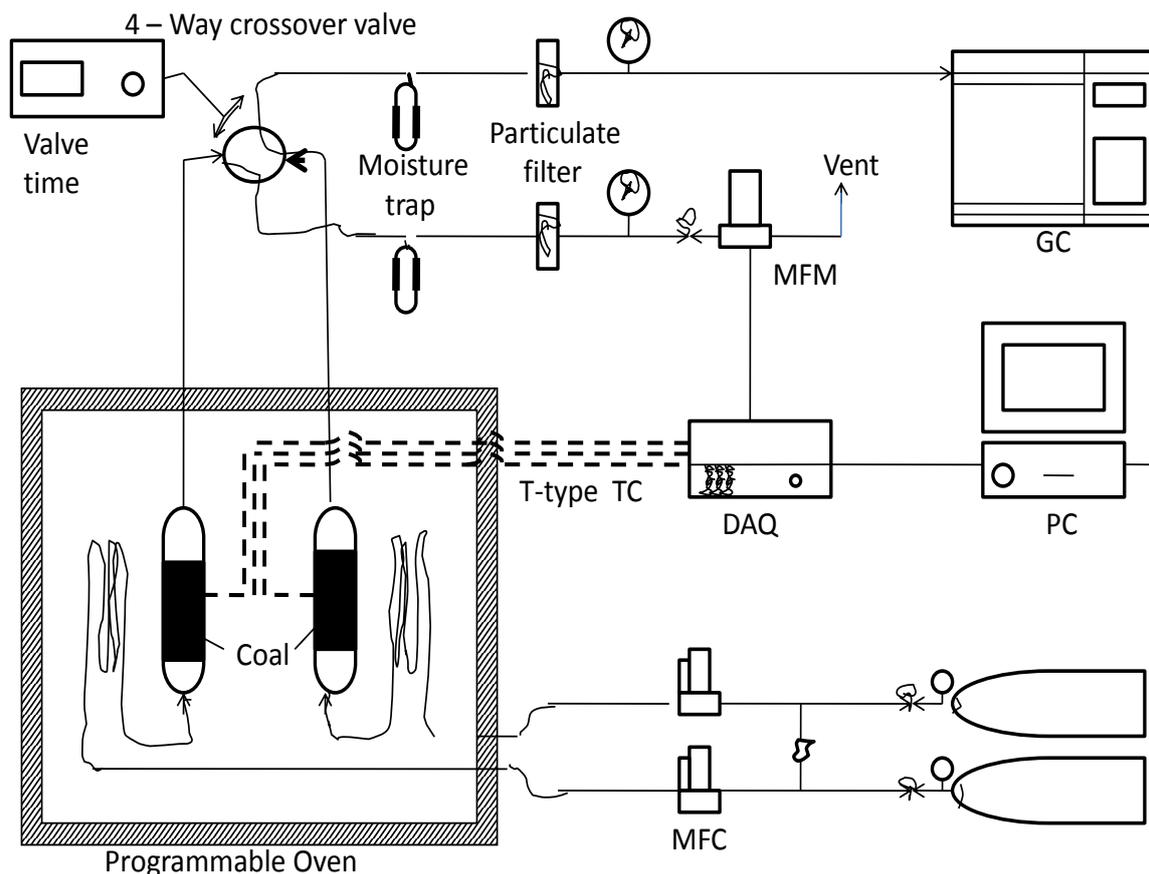


Fig. 5: Schematic diagram of experimental apparatus.

The vessels are sent to the GC 96890N, for measuring components, or the mass flow meter (MFM) for measuring the flow rate after reaction, according to the selected 4-way crossover valve location that changes periodically. The  $O_2$ , CO and  $CO_2$  gases emitted from each vessel were measured in the GC to which the thermal conductivity detector and two columns (60/80 Molecular Sieve 13X, 80/100 Parapak N, SUPELCO) are installed.

35g of the coal sample dried in each vessel was loaded and installed them inside the oven that was set at  $40^\circ C$ . Then, nitrogen gas of 75ml/min was supplied for two hours in order to cause the temperature to achieve equilibrium. When the temperature of the coal inside the vessel was  $40^\circ C$ , nitrogen

gas to one vessel of 75ml/min and the air to another vessel with the same flow rate and increased the oven temperature to  $180^\circ C$  by  $0.5^\circ C/min$ .

## RESULT AND DISCUSSION

Since the generation of heat is the main purpose of industrial combustion, the coal's calorific value or specific energy is of particular interest. The property is governed by the proportion between non-combustible (ash, water) and combustible matter in the coal. The latter consists mainly of the elements carbon, hydrogen and sulphur. The exothermic values of the reaction of these elements with oxygen differ quite considerably, hydrogen having the highest value. Variations in the elemental

composition of coals affect their heat values in response to changes in rank and type. One reason for an increase in calorific value during coalification is the decrease in the moisture content of lignite and sub-bituminous coals. The decline in the oxygen content during the transition from high-volatile to medium-volatile bituminous coals also contributes to an increase in calorific value. The latter peaks in the low-volatile bituminous coals but begins to drop again with the loss of much of its hydrogen as the coal approaches anthracite rank.

The infrared spectrum (Fig. 6) shows the principal functional groups related to organic matter include the aliphatics (2800 - 3200  $\text{cm}^{-1}$ ) and aromatics (800 - 1200  $\text{cm}^{-1}$ ). The response at 600-3800  $\text{cm}^{-1}$ , attributed the hydroxyl group, is also influenced by clay minerals and cannot be considered as wholly from organic matter. The principal application of infra-red spectroscopy is to evaluate the relative importance in organic matter of C=O and C-C functional groups (Tissot and Welte, 1984).

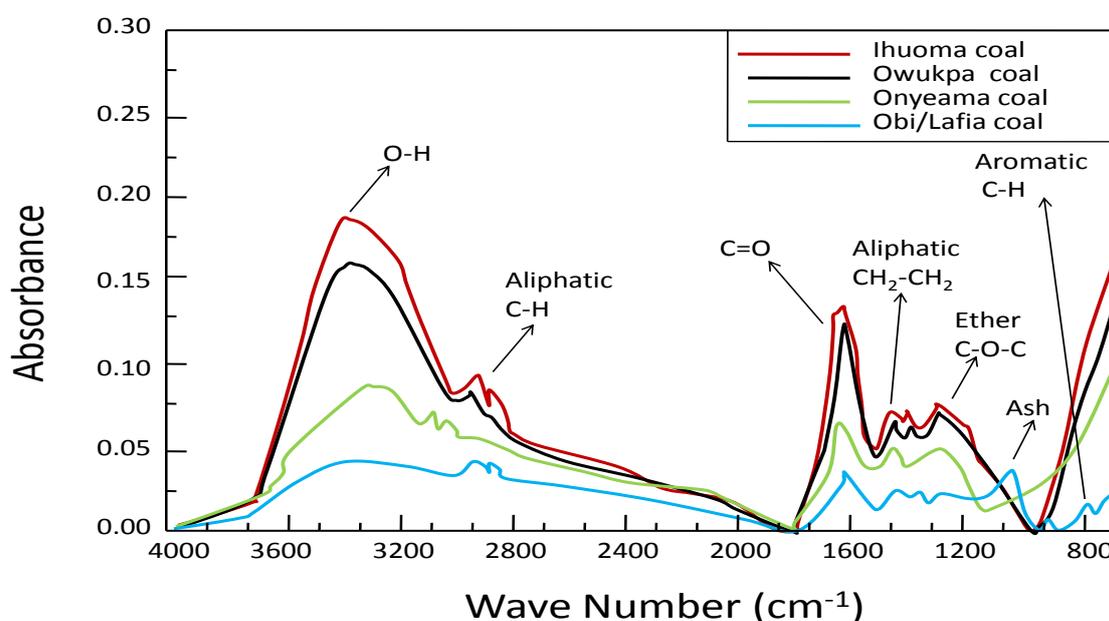


Fig. 6: FT-IR spectrum of coal from the Benue Trough.

Infrared spectrum shown in Fig. 6 is prominent functional groups related to organic matter include the hydroxyl groups at 3400 - 3500  $\text{cm}^{-1}$ , the aliphatic at 2800 - 3200  $\text{cm}^{-1}$  and 1400 - 1600  $\text{cm}^{-1}$ , as well as the aromatics at 1600 - 1700  $\text{cm}^{-1}$  and 700 - 850  $\text{cm}^{-1}$ . The C=O groups attributed to the spectral region of 1700 - 1710  $\text{cm}^{-1}$  [Mongenet *et al.*, 1999] are absent in Fig. 6, but some, attributed to 1040 - 1400  $\text{cm}^{-1}$  [Tissot and Welte, 1984], may be masked by the broad band attributed silicates. Both

the fact that the C=O groups have a high molecular absorption coefficient that is well resolved by FT-IR, and the low intensity of the 1700 - 1710  $\text{cm}^{-1}$  band relative to other functional groups with lower molecular absorption coefficient, indicate the presence of few carboxyl and carbonyl groups.

#### Properties of Samples

Table 1 shows the results of proximate analysis and calorific value analysis of the coal samples. The moisture content of the

lignite coal, Ihuoma coal was 36.55 wt%. The Onyeama coal and Owukpa coal, sub-bituminous coal, was 3.90 and 6.70 wt%, respectively. The Obi/Lafia coal, the bituminous coal, was 8.41 wt%. The content of volatile matter in Ihuoma coal (39.15 wt%) was higher than that of fixed carbon (20.34 wt%). However, the content of fixed carbon in Obi/Lafia coal (58.00 wt%) was higher than that of the Onyeama coal (41.20 wt%) and Owukpa coal (42.75 wt%) and

also was higher than that of the volatile matter; the fixed carbon showed a higher amount than volatile matter (31.83 wt%). As for the ashes, Obi/Lafia coal contained percentage of ash content and it was higher than Onyeama, Owukpa and Ihuoma coal samples, which contained 9.90, 7.92 and 4.07 wt%, respectively. It has been known that the lower the rank, the more the coal will have high moisture content and the higher the volatile matter compared to the higher rank coals.

Table 1: Proximate and calorific values of minimum, maximum and average for aggregate of each coal type.

Proximate Analysis (wt%)																	
Sample Name	Type	Locality	%Moisture Content			%Ash Content (wt)			%Volatile Matter (wt)			% Fixed Carbon			Calorific Values (kcal/kg) wt		
			Min.	Max.	Av.	Min.	Max.	Av.	Min.	Max.	Av.	Min.	Max.	Av.	Min.	Max.	Av.
ORLU	Lignite	Ihuoma	35.40	37.50	36.55	3.98	4.20	4.07	37.76	40.33	39.15	19.59	21.05	20.34	5098.00	5342.00	5189.75
ONYE	Sub-bituminous	Onyeama	3.15	4.15	3.90	3.16	21.18	9.90	43.39	47.30	45.07	32.28	47.48	41.20	6067.00	7621.80	7025.00
OWUK	Sub-bituminous	Owukpa	6.36	7.23	6.70	6.96	8.60	7.92	41.98	47.90	45.22	42.33	43.23	42.75	6430.00	6475.60	6433.15
OLAF	Bituminous	Obi/Lafia	7.20	8.93	8.41	12.30	14.70	13.93	31.65	32.23	31.83	57.65	58.23	58.00	7524.00	7745.00	7633.25

### The Mechanism of Spontaneous Combustion of Coal

Although many factors affect heat producing reactions, the oxidation of carbonaceous matter in coal of ambient temperatures is the major cause for the initiation of spontaneous combustion (Güney, 1968; Banerjee, 1985; Goodarzi and Gentzis, 1991; Wei et al., 2013).

The oxidation of coal, like all oxidation reactions, is exothermic in character. The exact mechanism of the reaction is still not well understood. However, scientists agree

that the nature of the interaction between coal and oxygen at very low temperatures is fully physical (adsorption) and changes into a chemisorption form starting from an ambient temperature (Münzner and Peters, 1965; Banerjee, 1985; Postzednik et al., 1988). The rate of oxygen consumption is extremely high during the first few days (particularly the first few hours) following the exposure of a fresh coal surface to the atmosphere. It then decreases very slowly without causing problems unless generated heat is allowed to accumulate in the

environment. Under certain conditions, the accumulation of heat cannot be prevented, and with sufficient oxygen supply, the process may reach higher stages.

The loose coal-oxygen-water complex formed during the initial stage (peroxy-complexes) decomposes above 70-85°C, yielding CO, CO<sub>2</sub> and H<sub>2</sub>O molecules. The rate of chemical reactions and exothermicity change with the rise in temperature, and radical changes take place, starting at about 100°C, mainly due to loss of moisture (Oresko, 1959; Banerjee, 1985; Handa et al., 1985; Kaymakçi and Didari, 2002). This process continues with the rise in temperature, yielding more stable coal-oxygen complexes until the critical temperature is reached. From then on, it is fairly safe to assume that an actual fire incident will result.

### **Factors Affecting the Spontaneous Combustion of Coal**

The main reason for the difficulties in understanding the mechanism of spontaneous combustion is the pressure of many internal and external factors affecting the initiation and development of the phenomenon (Table 2). These factors have been reviewed by various researchers (Kröger and Beier, 1962; Güney, 1968; Chamberlain and Hall, 1973a; Feng et al., 1973; Beier, 1973; Kim, 1977; Banerjee, 1982; Didari, 1988; Goodarzi and Gentzis, 1991; Didari and Ökten, 1994; Lang and Fubao, 2010; Xie et al., 2011). The main factors which have significant effect on the process according to Güney (1968) are summarized below:

- i) Pyrite content may accelerate spontaneous combustion,

**Table 2: Factors affecting the spontaneous combustion of coal (Güney, 1968)**

Intrinsic Factors (Nature of Coal)	Extrinsic Factors (Atmospheric, Geological and Mining Conditions)
i) Pyrites	i) Temperature
ii) Moisture	ii) Moisture
iii) Particle size and surface area	iii) Barometric pressure
iv) Rank and petrographic constituents	iv) Oxygen concentration
v) Chemical constituents	v) Bacteria
vi) Mineral matter	vi) Coal seam and surrounding strata
	vii) Method of working
	viii) Ventilation system and air flow rate
	ix) Timbering
	x) Roadways
ii) Changes in moisture content; i.e. the drying or wetting of coal, have apparent effects,	tendency of coal towards spontaneous combustion increases,
iii). As the particle size decreases and the exposed surface area increases, the	iv). It is widely recognized that lower rank coals are more susceptible to spontaneous combustion than higher

- rank coals. The abnormalities in this relationship may be attributed to the petrographic constituents of coal. This is because lower rank coals contain more liptinite (more hydrogen) that enhance increase in hydrocarbon generation than the higher rank coals which might lose some hydrogen on high maturity stage. Coals of high hydrogen contents are more prone to spontaneous combustion,
- v). Ash content generally decreases the liability of coal to spontaneous heating. Certain parts of the ash, such as lime, soda and iron compounds, may have an accelerating effect, while others, such as alumina and silica, produce a retarding effect. It is clear that some chemicals promote combustion while others inhibit its development. Also, it is known that oil shale bands adjoining coal seams play an important role in mine fires,
  - vi). The temperature of the underground atmosphere is a direct factor,
  - vii). The presence of faults and zones of weakness around faults may contribute to the danger by allowing air leakage into coal mass,
  - viii). Mining methods with partial extraction, in which part of the coal seam is left in the goaf and pillars (designed for several purposes), can contribute to the potential for spontaneous combustion,
  - ix). Air flow rate is a complex factor because an air supply provides oxygen while it carries away the heat produced. There is a critical air quantity which allows the coal to oxidize and also allows the generated heat to accumulate. Therefore, it favours the process,
  - x). High ventilation differentials and changes in the mine ventilation system also affect the development of the spontaneous combustion process.

According to Querol et al. (2008) oxidation of organic matter is mostly the main cause of coal self-ignition. When the ignition temperature of coal is reached, it starts to burn by spontaneous combustion (Gervet, 2007; Quintero et al., 2009). The temperature at which the coal oxidation reaction becomes self-sustaining and spontaneous combustion occurs generally depends on the type of coal and surrounding conditions of heat dissipation (Gervet, 2007; Wei et al., 2013). Although some authors found a relationship between maceral composition and the potential for spontaneous combustion of coal, a general rule is not clear (Querol et al., 2008; Wantaek et al., 2013). The coal oxidizes and self-heating is accelerated until the combustion occurs. With decreasing in coal rank, the tendency to the spontaneous combustion increases. For example, lignites and sub-bituminous coals from Orlu and Onyeama can begin their spontaneous combustion at 573 K, whereas bituminous coals as those of the Obi/Lafia coal mine at 873 K.

The results of this unique and comprehensive research are given in Table 1. Since the study is related to a specific coal region (Benue Trough), and any reported information on similar studies may not be available, a comparison equally may not be possible. Based on this reality, CPT can be taken as the major parameter to evaluate the relations. As seen in Fig. 1, there are high correlations between CPT and the volatile matter, ash, carbon of these coals from these areas (Orlu, Onyeama and Obia/Lafia) of the Benue Trough.

Kaymakçi and Didari (2002) demonstrated that through the linear regression analyses ash, volatile matter, carbon, hydrogen, exinite, inertinite and mineral matter are the major factors affecting spontaneous combustion. This report has confirmed the results that have been discussed for Table 1 and Fig. 1 above in which CPT has been correlated with all the proximate data obtained from this study. To further in confirming those realistic factor of CPT and proximate data obtained from coals of the Benue Trough through calculation of the multiple regression analyses Kaymakçi and Didari (2002), also found these major factors to be volatile matter, carbon, hydrogen, nitrogen, oxygen, sulphur and inertinite. With all these supportive and confirmative results and calculations a comparison of spontaneous combustion susceptibility of coals from Orlu, Onyeama and Obi/Lafia has been achieved through the recognition of these major factors.

There is no doubt that spontaneous combustion susceptibility has a negative impact in world coal deposits (such as the Benue trough coal mines) on mining operations, coal beneficiation and safety, health and environment of the mine and surrounding communities. CPT measurement in this study was conducted according to coal properties such as rank, moisture, ash, volatile matter contents, calorific value, and application conditions such as the flow rate of oxygen, heating rate, and the amount coal samples. From the results and discussions CPT has being taken as the major parameter to evaluate the relations of coal combustion susceptibility. It was found that there are high correlations between CPT and the volatile matter, ash, carbon of these coals from these areas (Orlu, Onyeama and Obia/Lafia) of the Benue Trough. With the recognition of these major

factors a comparison of spontaneous combustion susceptibility of coals from Orlu, Onyeama and Obi/Lafia has been achieved.

German Academic Exchange Services (DAAD) provided support and access to Proximate and Calorific laboratory facilities in Hannover, Germany. Dr. Hermann Wehner, George Scheeder and Jolanta Kus are thanked for supervision and generating data for this manuscript.

## REFERENCES

- Adeleye, D.R. and Fayose, E.A. (1978). Stratigraphy of the type section of Awe Formation, Odukpani area, southeastern Nigeria. *Nigerina Journal of Mining and Geology*, 15, 33-37.
- Akande, S.O. and Erdtmann, B.D. (1998). Burial metamorphism (thermal maturation) in Cretaceous sediments of the Southern Benue Trough and Anambra Basin, Nigeria. *AAPG Bulletin*, 82(6), 1191-1206.
- Akande, S.O., Ojo, O.J., Erdtmann, B.D. and Hetenyi, M., 1998. Paleoenvironments, source rock potential and thermal maturity of the Upper Benue rift basins, Nigeria: implications for hydrocarbon exploration. *Organic Geochemistry*, 29, 531-542.
- Akande, S.O., Ogunmoyero, I.B., Petersen, H.I. and Nytoft, H.P. (2007). Source rock evaluation of coals from the Lower Maastrichtian Mamu Formation, SE Nigeria. *Jour. Petrol. Geol.*, 30(4), 303-324.

- Banerjee, S.C. (1982). A theoretical design to the determination of risk index of spontaneous fires in coal mines. *Journal of Mines, Metals and Fuels*, 399-406.
- Banerjee, S.C. (1985). Spontaneous combustion of coal and Mine Fires. Oxford and IBH Publishing Company, India, 45-53.
- Beier, E. (1973). Einfluss von Feuchtigkeit, Eisensalsen und Mikroorganism auf die Atmosphärische Oxydation von Kohle und pyrit, *Glückauf Forschungshefte* 34, H.I, 24-32.
- Benkhelil, J., 1989. The evolution of the Cretaceous Benue Trough, Nigeria. *Journal of African Earth Sciences*, 8, 251-282.
- Carter, J. D., Barbar, W., Tait, E. A. and Jones, G. P., 1963. The geology of parts of Adamawa, Bauchi and Borno Provinces in northeastern Nigeria. *Geological Survey of Nigeria Bulletin*, 30, 1-108.
- Chamberlain, E.A.C. and Hall, D.A. (1973a). The liability of coals to spontaneous combustion. *Colliery Guardian*, 65-72.
- Didari, V. (1988). Developing a spontaneous combustion risk index for Turkish Coal Mines, Preliminary Studies. *Journal of Mines, Metals and Fuels*, 211-215.
- Didari, V., Kaymakçı, E. and Toroğlu, I. (1993). Kendiliğinden Yanmanın Araştırılmasında Kullanılabilir Bir Laboratuvar Deney Düzenliği, Türkiye 13. Madencilik Kongresi Bildiriler Kitabı, İstanbul, 69-98.
- Didari, V. and Kaymakçı, E. (1995). A laboratory set-up to be used in the study of spontaneous combustion of coal. *Turkish Journal of Engineering & Environmental Sciences*, 19(5), Ankara, 385-390
- Didari, V. and Ökten, G. (1994). Spontaneous combustion of coal and prevention methods. *Coal*, O. Kural, Ed., 215-221.
- Dike, E.F.C. (1993). Stratigraphy and structure of the Kerri-Kerri Basin, north-eastern Nigeria. *Journal of Mining and Geology*, 29 (2), 77-93.
- Enu, I. E. (1987). The palaeoenvironment of deposition of Late Maastrichtian to Paleocene black shale in the eastern Dahomey Basin, Nigeria. *Geology of Mijimbouw*, 66, 15-20
- Feng, K.K., Chakravorty, R.N. and Cochrane, T.S. (1973). Spontaneous combustion- A Coal Mining Hazards. *The Canadian Mining and Metallurgical Journal*, 75-84.
- Freeth, S.J. (1990). The origin of the Benue Trough. In: *The Benue Trough Structure and Evolution* (Edited by Ofoegbu, C.O). Vieweg and Sohn, Braunschweig, Germany. 217-227.
- Gervet. B., 2007. Coal Fire Emission Contributes to Global Warming. Renewable Energy Research Group Division of Architecture and Infrastructure. Lulea University of Technology SE-97187 Lulea, Sweden. 14pp.

- Goodarzi, F. and Gentzis, T. (1991). Geological controls on the self burning of coal seams. D.C. Peters, Ed., *Geology in Coal Resource Utilization*, Tech-Books, Fairfax, Virginia, pp. 181.
- Güney, M. (1968). Oxidation and spontaneous combustion of coal – Review of Individual Factors. *Colliery Guardian*, 216, 105-110
- Handa, T., Nishimoto, T., Morita, M. and Komada, J. (1985). Spontaneous combustion of coal (1), *Fire Science and Technology* 5, 21-30.
- Jauro, A., Obaje, N.G., Agho, M.O., Abubakar, M.B. and Tukur, A. (2007). Organic Geochemistry of Cretaceous Lamza and Chikila coals, Upper Benue Trough, Nigeria. *Fuel*, 86, 520-532.
- Kaymakçı, E. (1998). Zonguldak Havzasi kömür damarlarına Uygulanabilecek bir kendiliğinden Yanmaya Doğal Yatkılığı Değerlendirme Tekniğinin Geliştirilmesi. Doktora Tezi, ZKÜ Fen Bilimleri Enstitüsü, pp. 148.
- Kaymakçı, E. and Didari, V. (1992). Kömürün kendiliğinden Yanmaya Yatkınlığının Belirlenmesinde Kullanılan Kitabi. Zonguldak, pp. 129-140.
- Kaymakçı, E. and Didari, V. (2002). Relation between Coal Properties and Spontaneous Combustion Parameters. *Turkish Journal Engineering & Environmental Sciences* 26, 59-64.
- Kim, A.G. (1977). Laboratory studies on spontaneous heating of coal. US Bureau of Mines IC 8756.
- Kröger, C. and Beier, E. (1962). Die Vertwitterung von Steinkohlen. *Brennstoff-Chemie*, 11, 328-335.
- Lang, L. and Fu-bao, Z. (2010). A comprehensive hazard evaluation system for spontaneous combustion of coal in underground mining. *International Journal of Coal Geology* 82(1-2) 27-36.
- Münzner, H. und Peters, W. (1965). Zur Kinetik der Kohlenoxidation im Temperaturbereich 30-100°C. *Brennstoff-Chemie*, 12, 399-406.
- Obaje, N.G., Ulu, O.K. and Petters, S.W. (1999). Biostratigraphic and geochemical controls of hydrocarbon prospects in the Benue Trough and Anambra Basin, Nigeria. *Nig. Assoc. Petrol. Expl. Bull.*, 14(1), 18-54.
- Obaje, N.G., Abaa, S.I., Najime, T. and Suh, C.E. (1999). Economic geology of Nigeria coal resources – a brief review. *Africa Geosciences Review*, 6, 71-82.
- Obaje, N.G. and Hamza, H., 2000. Liquid hydrocarbon source-rock potential of mid Cretaceous coals and coal measures in the middle Benue trough of Nigeria. *International Journal of Earth Sciences*, 89, 130-139.
- Obaje, N.G., Wehner, H., Scheeder, G., Abubakar, M.B. and Jauro, A. (2004). Hydrocarbon prospectivity of Nigeria's inland basins: From the

- viewpoint of organic geochemistry and organic petrology. AAPG Bulletin, 87, 325-353.
- Obaje, N. G., Attah, D. O., Opeloye, S. A. and Moumouni, A. (2006), Geochemical evaluation of the hydrocarbon prospects of sedimentary basins in Northern Nigeria. *Geochemistry Journal*, 40, 227 – 243.
- Offodile, M. E. (1976). The geology of the Middle Benue, Nigeria. Special Volume, Palaeontological Institute University of Uppsala, 4, 1-166.
- Oresko, W.F. (1959). Die Gesetzmässigkeiten bei der Entwicklung eines Kohlenbrandes. *Bergbaujournal* 2, 74-80.
- Peason, M.J. and Obaje, N.G., 2000. Onocerane and other triterpenoids in Late Cretaceous sediments from the upper Benue trough of Nigeria: tectonic and paleoenvironmental implications. *Organic Geochemistry*, 30, 582-593.
- Petters, S. W. (1978). Stratigraphic evolution of the Benue Trough and its implications for the Upper Cretaceous paleogeography of West Africa. *Journal of Geology*, 86, 311-322.
- Petters, S. W. (1979). Maastrichtian arenaceous foraminifera from northwestern Nigeria. *Paleontology*, 22, 947-963.
- Petters, S. W. (1980). Biostratigraphy of upper Cretaceous foraminifera of the Benue Trough, Nigeria. *Journal of Foraminiferal Research.*, 10, 199-204.
- Petters, S. W. (1982). Central West Africa Cretaceous-Tertiary benthic foraminifera and stratigraphy. *Paleontology (A)* 179, 1-104.
- Petters, S. W. (1991). *Regional Geology of Africa*. Springer-Verlage, Berlin, 722pp.
- Postrzednik, S., Bialecki, R., Novak, A., Scholz, R. und Specht, E. (1988). Zur problematische der Selbsterwärmung fester Brennstoffe (1). *Erdöl-Erdgas Kohle*, Heft 2, 79-85.
- Querol, X., Izquierdo, M., Monfort, E., Alvarez, E., Font, O., Moreno, T., Alastuey, A., Zhuang, X., Lu, W., Wang, Y., 2008. Environmental characterization of burnt coal gangue banks at Yangquan, Shanxi Province, China. *Int. J. Coal Geol.* 75, 93-104.
- Quintero, J.A., Candela, S.A., Rios, C.A., Montes, C. and Uribe, C. (2009). Spontaneous combustion of the Upper Paleocene Cerrejon Formation coal and generation of clinker in La Guajira Peninsula (Caribbean Region of Colombia). *International Journal of Coal Geology*, 80, 196-210.
- Read, H. H. and Watson, J. (1978). *Introduction to Geology*, vol.2, Earth History. English Language Book Society and Macmillian, 232.
- Singh, R.N., Shonhardt, J.A. and Terezopoulos, N. (2002). A new

- dimension to studies of spontaneous combustion of coal. *Mineral Resources Engineering*, 11(2), pp 147.
- Taylor, G. H., Teichmüller, M., Davis, A., Diessel, C. F. K., Littke, R. and Robert, P. (1998). *Organic Petrology*. Gebrüder Bornträger, Berlin, Stuttgart, pp 25-502.
- Tissot, B. P. and Welte, D. H. (1984). *Petroleum Formation and Occurrence*, 2<sup>nd</sup> Ed. Springer-Verlag, Berlin, Heidelberg, New York, Tokyo, 699pp.
- Uzoegbu, M.U. (2010). Technological properties and hydrocarbon generative potential of Late Cretaceous coal deposits in the Anambra Basin, Nigeria. Unpublished Ph.D thesis, Abubakar Tafawa Balewa University, Bauchi.
- Uzoegbu, M.U. and Dike, E.F.C. (2009). Petrography and Technological Properties of Late Cretaceous Coals from the Anambra Basin, Nigeria. *Proc. for Nat. Cent. for Petrol. Res. and Dev., A.T.B.U., Bauchi on Sustainable Fossil Fuel and Renewable Energy in the Northeast and other Related Regions*, 2009; 63-80.
- Wantaek J. Hokyung C., Sangdo K., Jiho Y., Donghyuk C., Youngjoon R., Jeonghwan L. and Sihyun L. (2013). A comparison of spontaneous combustion susceptibility of coal according to its rank. *Korean Journal of Chemical Engineering*, 30 (5), 1034-1038
- Wei L., Yue-Ping Q., Yong-Jiang H., Tian-Zhu G. and Jing-Yan J. (2013). Minimum secure speed of fully mechanized coal face based on critical temperature of coal spontaneous combustion. *Journal of Coal Science and Engineering (China)*, 19 (2), 147-152.
- Whiteman, A. J. (1982). *Nigeria: its Petroleum Geology, Resources and Potential*. 1, 176pp; 2, 238pp. Graham and Trotman, London, UK.
- Xie, J., Xue, S., Cheng, W. and Wang, G. (2011). Early detection of spontaneous combustion of coal in underground coal mines with development of an ethylene enriching system. *International Journal of Coal Geology* 85:1, 123-127.